

Comment on "Dielectric behavior of paraelectric KTaO_3 , CaTiO_3 , and $(\text{Ln}_{1/2}\text{Na}_{1/2})\text{TiO}_3$ under a dc electric field"

A. Pashkin, V. Železný, M. Savinov and J. Petzelt
Institute of Physics, Academy of Sciences of the Czech Republic
Na Slovance 2, 182 21 Prague 8, Czech Republic

Chen Ang, Bhalla and Cross [Phys. Rev. B **64**, 184104 (2001)] have studied the low-frequency (20 Hz – 100 kHz) dielectric dispersion of the KTaO_3 crystal under a dc electric field. Performing fits of the electric field dependence they came to conclusion that an appreciable contribution to the dielectric permittivity originates from polar clusters. In this Comment we show that the dielectric permittivity at low frequencies (100 Hz – 1 MHz) equals to that in the THz region, close below the polar phonon response. This excludes the possibility of any appreciable dielectric dispersion due to polar clusters. In addition, we demonstrate that correct treatment using Landau-Ginzburg-Devonshire theory allows to fit the electric field dependence of the dielectric constant without assuming any polarization mechanism besides the polar phonon modes.

PACS numbers: 77.84.Dy, 77.80.Bh

The family of incipient ferroelectric materials with perovskite structure has attracted a great attention due to its high value of dielectric constant, low dielectric losses and high degree of tunability by the external electric field and temperature. The best known members of this family are SrTiO_3 (STO), KTaO_3 (KTO)¹ and CaTiO_3 (CTO)² which are also called "quantum paraelectrics". Microwave measurements of these materials by Rupprecht and Bell³ demonstrated that there is no sign of appreciable dielectric dispersion up to the GHz range. Therefore it is considered that dielectric properties of pure incipient ferroelectrics are determined by the contribution of the lowest polar-phonon mode (the soft-mode) whose frequency is decreasing on cooling roughly according to the Cochran law. Recently, combining the far infrared (FIR) spectroscopy with low-frequency (LF) dielectric measurements some of present authors confirmed the absence of appreciable dielectric dispersion below the soft-mode response in STO ceramics⁴ and CTO single crystals⁵.

Chen Ang, Bhalla and Cross in their paper⁶ investigated the dielectric response of KTO, CTO and $(\text{Ln}_{1/2}\text{Na}_{1/2})\text{TiO}_3$ ($\text{Ln} = \text{La}$ and Nd) (LNTO) under a strong dc electric field (up to 60 kV/cm). To describe the field dependence of the permittivity, they attempted to use an equation which is a simple polynomial expansion by even powers of electric field up to the fourth order. They were able to describe the field dependence in CTO and LNTO, but failed to perform a satisfactory fit for KTO. This fact brought the authors to conclusion that there should be another Langevin-type term describing the relaxational contribution of polar clusters to the total polarization. The final equation was of the form⁶

$$\epsilon(E) = \epsilon_1 - \epsilon_2 E^2 + \epsilon_3 E^4 + [P_r x / \epsilon(0)] [\cosh(Ex)]^{-2} \quad (1)$$

where $x = P_r L^3 E / 2k_B T$, P_r is the effective polarization of the polar clusters with the size L and k_B is the Boltzmann's constant. Using Eq. 1 to fit the measured

field dependence of the permittivity, they obtained the following parameters of polar clusters: $P_r = 0.4 \mu\text{C}/\text{cm}^2$, $L = 4.7 - 6 \text{ nm}$ and $\Delta\epsilon_{\text{cluster}} = 656$ (at 14 K). This would mean that 23% of the total dielectric response at low frequencies are due to some relaxational dispersion of polar clusters below the soft-mode response.

In the following we will show that our recent FIR and LF dielectric measurements of KTO exclude the possibility of any appreciable contribution to the LF permittivity besides the contribution of the soft phonon mode. Moreover we will demonstrate that a correct treatment using the Landau-Ginzburg-Devonshire thermodynamic theory allows to describe the field dependence of the dielectric constant in KTO without using additional Langevin-type terms.

Our measurements have been performed on nominally pure KTO single crystals⁷. The samples were prepared in the form of thin $\langle 001 \rangle$ -oriented plane-parallel plates with dimensions of $7 \times 7 \times 0.2 \text{ mm}^3$. LF dielectric measurements were carried out using a HP 4192A impedance analyzer in the frequency range 100 Hz – 1 MHz with gold electrodes deposited on the main surfaces of the sample. The FIR reflectivity was measured with Bruker IFS 113v Fourier Transform spectrometer in the range 30 – 650 cm^{-1} . The complex dielectric function in the frequency range 5 – 30 cm^{-1} was obtained by means of time-domain THz transmission spectroscopy on a 65 μm thick plane-parallel sample. The frequencies of the three polar phonon modes and their contribution to the dielectric function were obtained from the fit to the FIR reflectivity using the factorized form of the model dielectric function combined with the directly measured values of the THz complex permittivity⁸. The temperature dependence of the soft-mode frequency was found to be in perfect agreement with the hyper-Raman data⁹.

In Fig. 1 the measured permittivity at 43.5 kHz is compared with the low-frequency limit of our fitted FIR dielectric function. The permittivity data from Ref. 6 are also added for comparison. One can observe good agree-

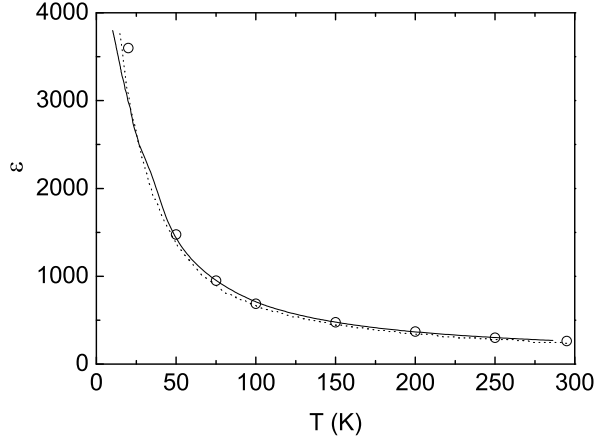


FIG. 1: Permittivity of KTaO₃ crystal at 43.5 kHz (full line), LF permittivity data taken from Ref. 6 (dotted line) and contribution of the polar-phonon modes (open circles).

ment between LF permittivities of KTO crystals and between LF and FIR permittivities in the whole measured temperature range. Somewhat higher value of FIR permittivity compared to the LF values at 20 K lies within the instrumental errors. Anyway, Fig. 1 clearly shows that at all measured temperatures there is no space for any appreciable dispersion below the soft-mode response down to kHz range.

To demonstrate the fitting of the field dependence of permittivity, following Fleury and Worlock¹⁰ let us expand the crystal free energy per unit volume in a power series of lattice polarization:

$$G = G_0 + \frac{1}{2}\chi(T)(P_x^2 + P_y^2 + P_z^2) + \frac{1}{4}\xi(P_x^4 + P_y^4 + P_z^4) + \frac{1}{2}\xi'(P_x^2 P_y^2 + P_y^2 P_z^2 + P_x^2 P_z^2) + \frac{1}{6}\zeta(P_x^6 + P_y^6 + P_z^6) + \text{other sixth-order terms} + \dots \quad (2)$$

In our case polarization has only one component directed along the z-axis ($P_x = P_y = 0$). Thus we can obtain relation between the electric field and polarization:

$$E_z = (\partial G / \partial P_z)_T = \chi(T)P_z + \xi P_z^3 + \zeta P_z^5 + \dots \quad (3)$$

which is a special case of the general relation for arbitrary polarization^{10,11}. Then one can derive the expression for the inverse susceptibility:

$$\left(\frac{1}{\epsilon_0[\epsilon(T, E) - 1]} \right)_{zz} = \partial E_z / \partial P_z = \chi(T) + 3\xi P_z^2 + 5\zeta P_z^4 + \dots \quad (4)$$

Here $\chi(T) = 1/\epsilon_0[\epsilon(T, 0) - 1]$ is the inverse susceptibility in the zero bias field and $\epsilon_0 = 8.85 \cdot 10^{-12}$ F/m is the permittivity of vacuum. To calculate the permittivity under dc bias field, one has to use Eq. 3 to calculate the polarization and then insert it into Eq. 4. The calculations

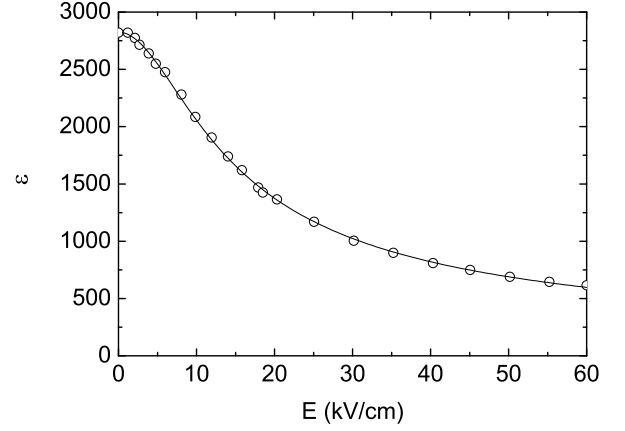


FIG. 2: Bias electric-field dependence of the KTaO₃ permittivity at 14 K taken from Ref. 6 (the first run). Full line corresponds to the fit using Eq. 3 and 4.

should be performed numerically because Eq. 3 is a *non-linear* polynomial equation of the 5-th order. Therefore the analytical expression given in Ref. 6 cannot be valid for highly anharmonic crystals and can be applied only in the weak field approximation. This approximation apparently holds in the case of CTO and LNTTO because of their weak nonlinearity for bias fields $E < 60$ kV/cm. However, in the case of KTO the lattice anharmonicity is essential. The fit using Eq. 3 and 4 of KTO permittivity under the dc electric field at 14 K taken from Ref. 6 (the first run of measurements) is shown in Fig. 2. The fit uses two independent parameters $\xi = 10^{10}$ and $\zeta = 10^{11}$ in SI units and the value $\epsilon(14 \text{ K}, 0) = 2821$ taken from Ref. 6. The fitted nonlinear coefficients are in reasonable agreement with the previously published data (see Ref. 10 and references therein). Fig. 2 demonstrates that the expansion up to the 6-th order in Eq. 2 is sufficient to ensure a good agreement between the theory and experiment.

The critical limit for the weak field approximation can be found from the condition that 4-th and 6-th order terms in Eq. 2 are small compared to the quadratic term

$$\xi P_{cr}^2 + \zeta P_{cr}^4 = \lambda \chi, \quad (5)$$

where $\lambda \ll 1$ is a dimensionless constant. For the typical values of nonlinear coefficients¹⁰ we can neglect the 4-th order term in Eq. 5 and using Eq. 3 we obtain

$$E_{cr} = \chi \sqrt{\frac{\lambda \chi}{\xi}}. \quad (6)$$

Using our fit parameters for KTO and $\lambda = 0.1$ we calculate $E_{cr} \simeq 1.3$ kV/cm. One can see that this value is much smaller than the highest dc electric field in Ref. 6 (60 kV/cm).

It is believed that polar nano-clusters are induced by unavoidable dipolar impurities in nominally pure KTO¹².

The presence of such clusters appears in the LF dielectric spectra of KTO as a universal low-temperature dielectric dispersion⁷ with thermally activated behavior. Below 30 K this dielectric dispersion shifts below the frequency range of conventional LF dielectric spectroscopy. Dielectric spectroscopy can only establish that the contribution to permittivity of polar clusters is very small comparing to the phonon contribution above 30 K and cannot be observed in LF dielectric spectra below 30 K. On the other hand, the polar clusters can be detected by light scattering as it has been done in Raman¹³ and hyper-Raman¹² scattering experiments. These experiments, however, bring no information about the dynamics of the clusters because their relaxation is quasi-static comparing to the frequencies resolved in the light scattering experiments. The local lattice symmetry breaking due to the polar clusters relaxes the selection rules and induces activation of new lines. These changes are in agreement with existence of the polar clusters and do not contradict with our dielectric spectroscopy results.

Taking into account all the mentioned arguments, we can conclude that the estimated size of polar clusters

found in Ref. 6 does not have any reliable physical background and its possible correspondence with the Raman results¹³ is accidental.

Analysis of the field dependence of permittivity using equation similar to Eq. 1 was previously applied also to $\text{Sr}_{1-x}\text{Ca}_x\text{TiO}_3$ system^{14,15} where, due to the Ca-doping, appreciable dielectric dispersion indeed exists. However, the applied electric fields were much smaller ($E < 1$ kV/cm) than those in Ref. 6. Estimation of the critical electric field from Eq. 6 gives for STO $E_{cr} \simeq 0.2$ kV/cm (nonlinear parameters are taken from Ref. 10). Thus even 1 kV/cm field can introduce some error if one uses Eq. 1. In our opinion, the correct thermodynamic approach described here is always preferable for the analysis of nonlinear behavior under strong electric fields.

This work was supported by the Grant Agency of the Czech Republic (projects No. 202/01/0612 and 202/02/0238) and Czech Academy of Sciences (project AVOZ-010-914).

-
- ¹ G. A. Samara, *Solid State Physics*, vol. 56 (Academic, New York, 2001).
 - ² V. V. Lemanov, A. V. Sotnikov, E. P. Smirnova, M. Wehnacht, and R. Kunze, *Solid State Commun.* **110**, 611 (1999).
 - ³ G. Rupprecht and R. O. Bell, *Phys. Rev.* **135**, A748 (1964).
 - ⁴ J. Petzelt, T. Ostapchuk, I. Gregora, I. Rychetský, S. Hoffmann-Eifert, A. V. Pronin, Y. Yuzyuk, B. P. Gorshunov, S. Kamba, V. Bovtun, et al., *Phys. Rev. B* **64**, 184111 (2001).
 - ⁵ V. Železny, E. Cockayne, J. Petzelt, M. F. Limonov, D. E. Usvyat, V. V. Lemanov, and A. A. Volkov, *Phys. Rev. B* **66**, 224303 (2002).
 - ⁶ Chen Ang, A. S. Bhalla, and L. E. Cross, *Phys. Rev. B* **64**, 184104 (2001).
 - ⁷ V. A. Trepakov, M. E. Savinov, P. P. Syrnikov, S. Kapphan, A. Badalyan, V. Vikhnin, and L. Jastrabik, *Ferro-*

- electrics* **239**, 1159 (2000).
- ⁸ S. Kamba, P. Samoukhina, F. Kadlec, J. Pokorný, J. Petzelt, I. M. Reaney, and P. L. Wise, *J. Eur. Ceram. Soc.* **23**, 2639 (2003).
- ⁹ H. Vogt, *J. Phys.: Condens. Matter* **7**, 5913 (1995).
- ¹⁰ P. A. Fleury and J. M. Worlock, *Phys. Rev.* **174**, 613 (1968).
- ¹¹ W. N. Lawless, *Phys. Rev. B* **18**, 2394 (1978).
- ¹² H. Vogt, *J. Phys.: Condens. Matter* **3**, 3697 (1991).
- ¹³ H. Uwe, K. B. Lyons, H. L. Carter, and P. A. Fleury, *Phys. Rev. B* **33**, 6436 (1986).
- ¹⁴ J. Dec, W. Kleemann, U. Bianchi, and J. G. Bednorz, *Europhys. Lett.* **29**, 31 (1995).
- ¹⁵ U. Bianchi, J. Dec, W. Kleemann, and J. G. Bednorz, *Phys. Rev. B* **51**, 8737 (1995).